




International Journal of
Mechanical Engineering Research and Technology

ISSN 2454-535X

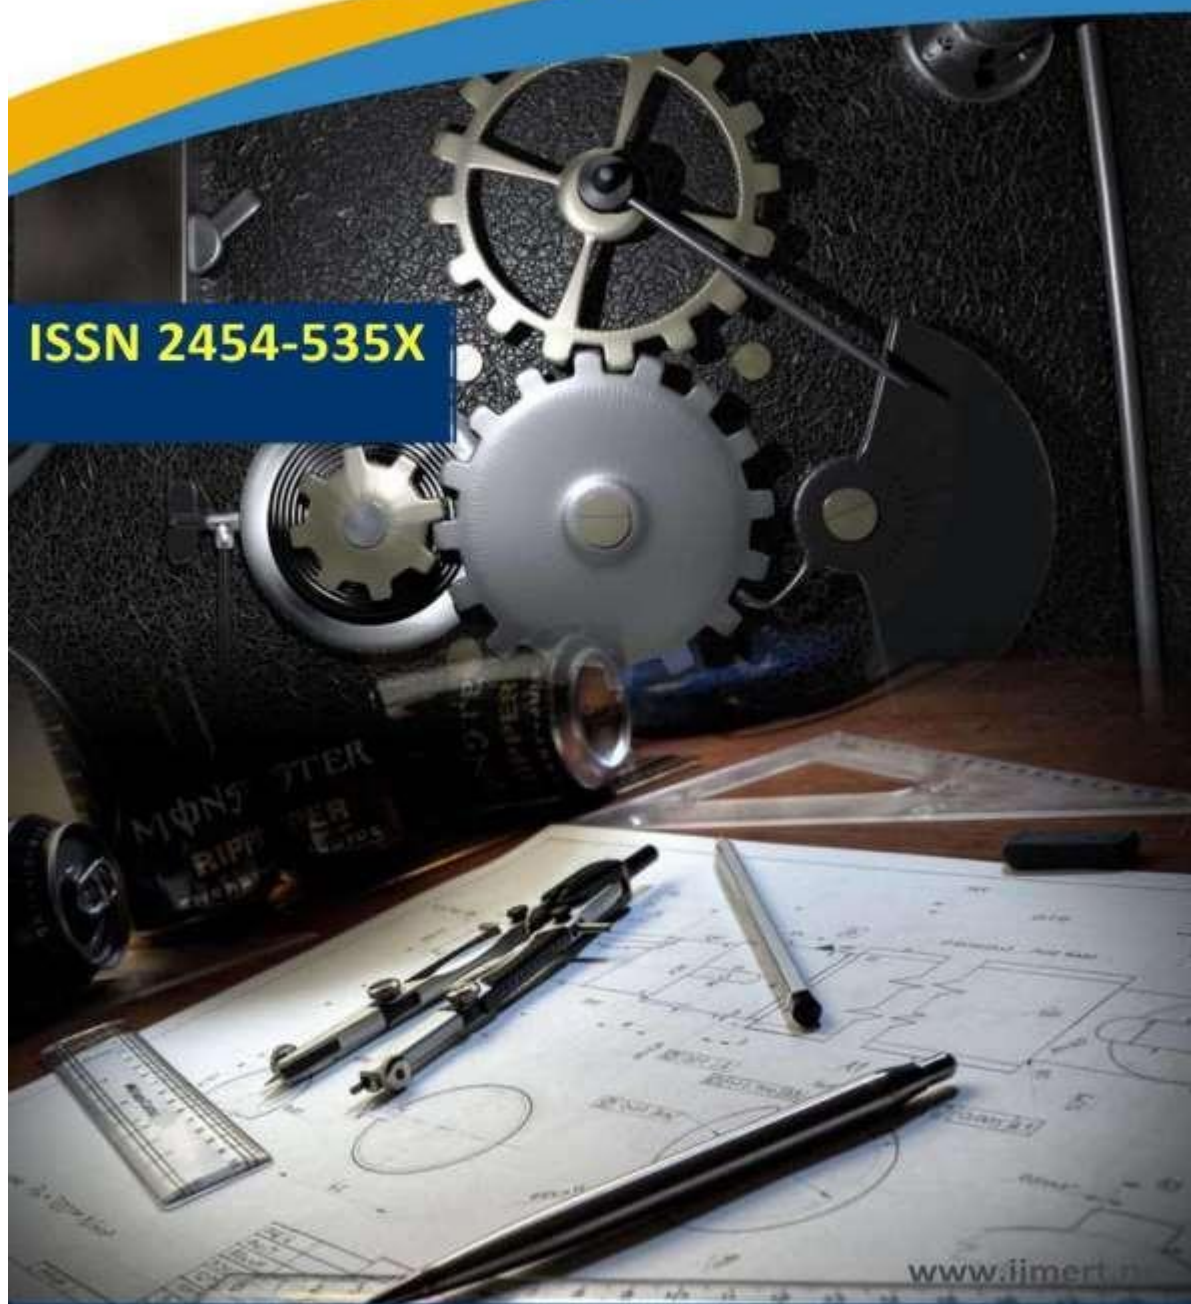

www.ijmert.net

Email ID: info.ijmert@gmail.com or editor@ijmert.net

Aluminum Alloys 6061 and 2024: Effect of Heat Treatment on Mechanical and Vibration Properties

Sonu Kapoor¹, Mohammed Rahim², Syed Firdose³, Mohamed Wajid⁴

[†]Department of Mechanical Engineering, Faculty of Engineering, University of Baghdad, Iraq

[‡]Department of Mechanical Engineering, Faculty of Engineering, Al-Nahrain University, Iraq

^{††}Department of Mechanical Engineering, Faculty of Engineering, University of Kufa, Iraq

E-mail: wajid.khan50@uokufa.edu.iq

ABSTRACT:

In order to study the effects of heat treatments, this paper examines the relationship between mechanical properties (yield and ultimate strength, elongation, hardness, and modulus of elasticity) and dynamic characteristics (natural frequency and dynamic response) for 6061 and 2024 aluminum alloys under impulse loading. Several strategies were used to carry out the study. The initial phase involved experimentally

determining the mechanical characteristics and natural frequency for the aluminum alloys after they had undergone various heat treatment techniques. In the second section of his research, an aluminum plate's natural frequency was computed numerically (using a finite element approach), and the results were compared to those obtained experimentally.

KEYWORDS: Heat Treatment; Aluminum Alloy; Vibration Plate; Impulse Load

INTRODUCTION

Since the 1930's aluminum alloys have been the principle material for aircraft fabrication. Aeronautical manufacturing depends greatly on 2xxx and 7xxx alloys. Presently there is a growing interest in 6xxx aluminum alloys due to its numerous beneficial qualities i.e. medium strength, formability, weldability, corrosion resistance, and low cost. In addition to its wide field of aircraft fabrication which include the fuselage for aircrafts, body panels for automobiles and their bumpers as a substitute ,after suitable heat treatment, for the more expensive 2xxx & 7xxx alloys. Owing to this the fabrication method and characteristics plays an important role. [1].

Aluminum alloys are divided into two groups and they are: those that cannot be heat treated, and

those that can. Those that are heat treatable can be hardened by the addition of certain alloying elements, and these elements are copper, zinc, magnesium and silicon, these elements when applied in different concentrations form compositions that display a solubility increase in aluminum at elevated temperatures it is possible conduct heat treatment on them. The process consists of heating the solution followed by quenching or aging. Conducting an appropriate sequence an agreeable ductility with a high strength can be obtained, [2]. Due the scientific importance of the 6xxx aluminum group they have undergone intensive studies because of their ability to increase in strength when subjected to precipitation hardening. These alloys are used in

extrusion, construction and automobile manufacturing, because of their low density which makes them simple to shape. In addition to them being low priced they have good weld ability and good corrosion resistance making them desirable, [3].

Different precipitants can be obtained depending on the type of constituents that the alloy is formed of. This will in turn influence and produce different mechanical properties, [4]. An attempt was made for positioning these precipitates on the phase diagram, via using the precipitates line chart, and the phases that are stable were detected. So as to acquire the best mechanical properties appropriate fabrication process is

Effects of Heat Treatment

Age hardening is a heat treatment method implemented on heat treatable aluminum alloys in order to improve some their mechanical properties. the process rearranges the components that make up the alloy that detach from the aluminum during the cooling phase after it had been heated to a specific temperature during the process, the alloy's elements that are dissolvable will compose a uniform mass by solid diffusion. The alloy is quenched so as to keep the uniform condition in the quenched state. This process produces a malleable supersaturated but insecure alloy. At room temperature, the alloying elements that form the alloy will start to precipitate from the solid solution, this will cause the alloy's hardness increase considerably. Some alloys need years in order to obtain strength and maximum hardness.

The alloys that have a slower transformation for age hardening can be sped up artificially by heating the alloy to a specific temperature and length of time depending on its dimensions, [7]. A considerable rise in yield and tensile strength is noted together with a decrease in ductility when it is subjected, after solution heat treatment, and cold work. Different compositions produce a variation of properties. Annealing is a heat treatment process used for recrystallization and/or eliminating residual stresses which are induced as a result of cold work and heat treatment. Annealing temperature for most of these alloys

needed to be chosen. The time needed for aging, temperature, occurrence of deformation and the whole fabrication process are also needed to be taken into consideration, [5]. The significance of the time spent between solution heat treatment and aging, artificially will demonstrate that the time spent from quenching till aging will lead to the natural aging of the specimen and hence lowering its hardness in the end. In another study, [6], deformed samples between quenching and aging and they concluded that this method has positive effects on hardness and strength.

reach 650 °F (343 °C). they are heated at a controlled pace depending on the thickness and which of the several types of annealing desired. The rate at which the part is cooled is not significant so long as it is not quenched as this will lead to residual stresses. [8].



Effects of Quenching

Quenching is when a metal is heated to a high temperature and then followed by rapid cooling as fast as possible by immersing the heated part in a relatively colder liquid such as oil or water. This process leads to an increase in the alloy's strength and resistance to corrosion. The alloy's structures as well as the elements that make up the alloy just prior to quenching are arrested when it is quenched. The alloy's properties are ruled by the alloy's constituents as well as its properties its cross-section's thickness and the cooling rate when the alloy is quenched which depends on the quenching medium's type and temperature.

Maximum corrosion resistance can be obtained as a result of quenching in cold water and is implemented on products fabricated by tube sheet, extrusions. Quenching by oil is favored to a less severe quench in which the mechanical properties are increased. Slower quenching in mediums such as boiling water is implemented on large sections and/or hefty forgings. A low quenching rate has a more homogeneous cooling rate and produces a less distorted and cracked product which usually occurs from uneven cooling. The temperature of the medium does not affect the resistance to corrosion; keep in mind the resistance to corrosion is less serious in thick parts than it is in thin parts. [9]. Since temperature has a significant effect on the mechanical properties, [10-14], and also since application of aluminum alloys are widely used; therefore it is a necessity to study the effect of heat treatment on aluminum alloys.

EXPERIMENTAL WORK

The experimental work was conducted on two types of aluminum alloys for this study, 6061-T6 and 2024-T4 alloys (chemical composition of the two alloys is shown in table (1). The work was divided into two parts. The first part was dedicated to evaluating the effect of heat treatment, for various temperatures, on the mechanical properties for aluminum alloys. Whilst in the second part the vibration characterizations for plate structure with various temperatures effect was determined in addition to these the basic mechanical properties: yield strength, ultimate stress, elongation, and, modulus of elasticity were measured. Also, the natural frequencies of a plate fabricated from these alloys were measured vibration characterizations measurement is the natural frequency of plate structure manufactured from its alloy materials, before and after heat treatment, by using vibration rig compound.

Table 1. Chemical composition of the alloys, % wt.

	Alloy	
	6061	2024
Si	0.78	0.37
Mg	1.08	1.5
Mn	0.15	0.6
Cu	0.36	4.4
Fe	0.16	0.4
Zn	0.053	0.21
Ni	0.007	----
Cr	0.35	0.1
Ti	0.025	0.09

Annealing Heat Treatment

The first thing we need to do is to eliminate all residual effects of any prior heat treatment that the plates may have been subjected to, its history was unknown this was achieved by placing both types of alloys in the form of plates in a furnace with the temperature set at (413 °C), they were soaked at this temperature for two hours. They were then left in the furnace to cool down slowly until they had reached (250 °C) and then onto room temperature. The process will present stress free plates (6061-T0) and (2024-T0) aluminum alloy plates

Solution Heat Treatment

Solution heat treatment is a process where a series of heating and rapid cooling are performed on the aluminum alloys. The heat treatment can be summarized as follows:

1. Heated to a specific temperature
2. Soaked at this temperature for a specific time
3. Rapidly quenched

Aluminum alloy 6061-T0 was heated in furnace at (530°C) for a period of one hour, after which the alloy was quenched in water and returned to the furnace to be heated to (175 °C) for a period of (3 hours) to ensure diffusion of copper atoms into the aluminum, [15-16]. At the end of this process, we obtained the aluminum alloy (6061- T4).

Aluminum alloy 2024-T0 had been heated in the furnace up to (494°C) for a period of (35 minutes). At the end of this time, it was quenched in water and returned to the furnace and heated up to (100 °C) for a period of (3-4 Hours) after this time had elapsed, we were able to obtain (AGING) tensile test specimens were made from the two prepared alloys in tested their harness and tensile strength mechanical properties of the examined alloys.

Solution Heat Treatment

Solution heat treatment is a process where a series of heating and rapid cooling are performed on the aluminum alloys. The heat treatment can be summarized as follows:

4. Heated to a specific temperature
5. Soaked at this temperature for a specific time
6. Rapidly quenched

Aluminum alloy 6061-T0 was heated in furnace at (530°C) for a period of one hour, after which the alloy was quenched in water and returned to the furnace to be heated to (175 °C) for a period of (3 hours) to ensure diffusion of copper atoms into the aluminum, [15-16]. At the end of this process, we obtained the aluminum alloy (6061- T4).

Aluminum alloy 2024-T0 had been heated in the furnace up to (494°C) for a period of (35 minutes). At the end of this time, it was quenched in water and returned to the furnace and heated up to (100 °C) for a period of (3-4 Hours) after this time had elapsed, we were able to obtain (AGING) tensile test specimens were made from the two prepared alloys in tested their harness and tensile strength mechanical properties of the examined alloys.

Vibration Test

Vibration tests were also conducted to find their natural frequency by using a vibration rig which was composed of the following devices, [17-21], as shown in Fig. 1


1. Plate sample
2. Structure rig
3. Supported for plate
4. Accelerometer
5. Amplifiers
6. Oscilloscope

The vibration signal was read from the oscilloscope by using the FFT technique, [22-27], the natural frequency for a plate can be calculated, as shown in Fig. 2. Where, the plate tested had the dimensions, (210*80*3 mm),




and supported as a simply supported & cantilever plate.

Figure 1. Vibration Rig Compound

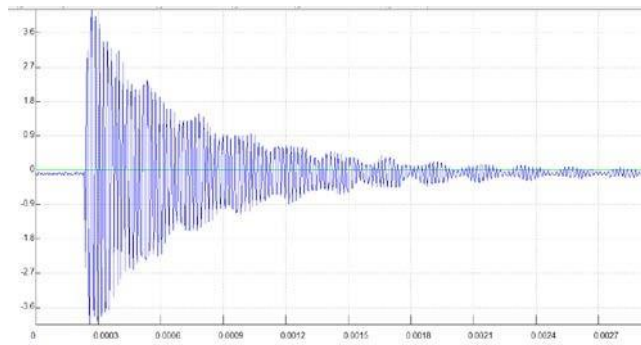

a. Vibration Response Signal (mv) with Time (sec) Relationship

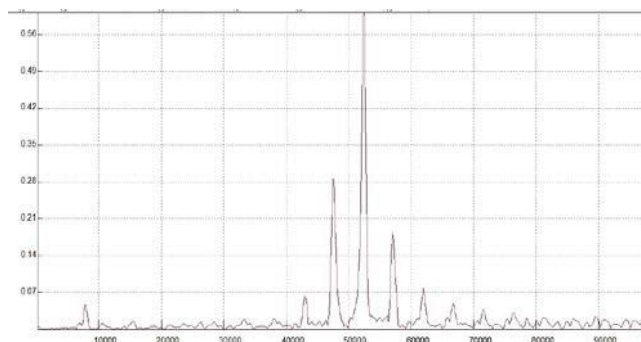

b. Vibration Response Signal (mv) with Frequency (Hz) Relationship

Figure 2. FFT for Vibration Response Signal

ANALYTICAL TECHNIQUE

The analytical analysis included drive and solution for general equation of motion, [28-30], for vibration plate structure applied to transverse impulse loading. Where the analysis included the solution for simply supported plate structure. Therefore, the hypothesized theory of plate vibration is the "Small Deflection Plate Theory", [31].

Then, the equilibrium equation in z-direction for transverse plate vibration is, $D(\nabla^4 w + 2\nabla^2 w + \nabla^4 w) + \rho h \frac{\partial^2 w}{\partial t^2} = f(x, y, t)$ (1) Where, $\nabla^4 = \frac{\partial^4}{\partial x^4} + \frac{\partial^4}{\partial y^4} + 2\frac{\partial^4}{\partial x^2 \partial y^2}$, $D = \frac{Eh^3}{12(1-\nu^2)}$, for, E: modulus of elasticity, ν : Poisson's ratio, h: plate thickness,

ρ : material density, $w(x, y, t)$: transverse plate deflection, and, $f(x, y, t)$: applied load per unit plate area. Then, to solve Eq. (1), to evaluate the natural frequency and the plate response, first evaluating the mode behavior for plate as a function of (x,y) by applying boundary conditions of plate, [32-33]. There, by applying boundary condition for plate structure supported as simply supported, get the shape function for first mode plate behavior as, $w(x, y) = A \sin \frac{\pi x}{a} \sin \frac{\pi y}{b}$ (2) Where, a and b are length and width for plate structure, and A constant. Then, by substituting Eq. 2 in to Eq. 1, and then multiplying the result by shape function of plate, using normalized method, [31],

$\int_0^a \int_0^b \rho h w^2 dx dy = 1$ (3) $\int_0^a \int_0^b$ Then, from Eq. 3 given, $A = \frac{2}{\sqrt{ab}}$ (4) Therefore, get, $\ddot{w}(t) + \omega^2 w(t) = N(t)$ (5) Where, $N(t) = \frac{2}{\sqrt{ab}} \int_0^a \int_0^b f(x, y, t) \sin \frac{\pi x}{a} \sin \frac{\pi y}{b} dx dy$ (6) And, $\omega = \pi^2 \sqrt{\frac{D}{\rho h}}$ (7) Then, by applying concentrated load on plate, get,

$N(t) = \frac{2}{\sqrt{ab}} F \delta(x-a/2) \delta(y-b/2) \delta(t)$ (8) Then, by using convolution integral, [34], and applying unit impulse load, get the response for plate structure by, $w(t) = \frac{2}{\omega \sqrt{ab}} \sin \omega t$ (9) Thus, from the analytical solution the natural frequency can be evaluated for simply supported plate and the time response for late subjected to impulse loading, by using Eqns. 7 and 9, respectively, with various heat treatment effect of aluminum materials plate. Where, the



mechanical properties for aluminum materials, with various heat treatment effect, can be used in the experimental mechanical properties calculation, [35-36]. Therefore, for agreement the experimental and numerical results were calculated, the analytical natural frequency results compared with experimental and numerical methods, and the analytical vibration time response compared with the numerical method.

NUMERICAL TECHNIQUE

The numerical method is an important method used to give approximate results and compared with other experimental and analytical results to give agreement for results calculated by other methods. There are several theories that give numerical analysis, but for dynamic behavior and rigid radicalization of structures, a finite element can be used to produce acceptable and reliable results, [37-40].

Any structure subjected for analysis by using the finite element method, the type of element must be selected for analysis, which depends on the structure geometry and problem application, then the mechanical properties for structure is then required which can be taken from the experimental work, and then, applying the load and solving the problem for structure. Thus, the element type that can be used for plate vibration is (Shell 281), [27], in which the element has six degrees of freedom in addition to other dynamic characteristics. Then, after selecting the element types must be mesh the structure to select the best number for element, after this the load is applied and solve the problem selected. Then the results are evaluated by numerical method the natural frequency and time response of platelets that are exposed to an impulse load, after which the natural frequency's results are then compared with that of those obtained experimentally and theoretically results of the process and theoretical. Also the plate's response to time is compared with the theoretical results that were obtained [41, 42].




RESULT AND DISCUSSION

The results for this paper was divided into two parts, the first is the mechanical properties for materials, whilst the second was for the dynamic characteristics for plate structure supported as a simply supported plate and cantilever plate, which included the natural frequency and the time response for plate subjected to an impulse load. Results were calculated for two aluminum alloys (6061 and 2024 alloy) with the effect of various heat treatments.

Mechanical Properties for Materials

The mechanical properties for 2024 and 6061 aluminum alloy calculated, with the effect of various heat treatment, are

1. Hardness
2. Yield strength
3. Ultimate strength
4. Modulus of elasticity
5. Elongation Where, its properties presenting through Figs. 3 to 17, there, Figs. 3 and 4 show the effect of heat treatment on the hardness for two types of aluminum alloys used, respectively, Fig. 5 shows the comparison for hardness with heat treatment effect between alloys 2024 and 6061. Then, Figs. 6 and 7 show the behavior for yield strength with heat treatment effect for the two types of alloys, also, Fig. 8 gives a comparison on the effect for heat treatment on the yield strength for two alloys. Also, Figs. 9 and 10 present the relationship between the ultimate strength and heat treatment, then, Fig. 11, presents the

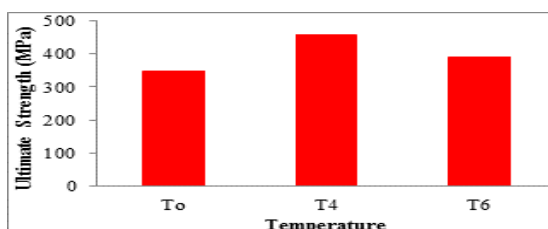

comparison for two alloys with heat treatment effect. In addition, Figs. 12 and 13 show the effect of heat treatment on the modulus of elasticity of two alloys types used, respectively, and, Fig. 14 shows the comparison between the 2024 and 6061 alloy with heat treatment

effect. Therefore, from Figs. 3 to 14 it can be seen that heat treatment increases the properties presented with best temperature at T4 for alloy 2024, but its properties increased with T6 more than the other temperature for alloy 6061. Also,

6. from this figure it can also be seen that heat treatment modifies its properties for 2024 alloy more than modifying the same properties 6061 aluminum alloy. Finally, Figs. 15 and 16 show the elongation for 2024 and 6061 aluminum alloy materials with heat treatment alloy, and the comparison between elongation for its materials is shown in Fig. 17. Where, from these figures can be seen that heat treatment decreases elongation for these two types of alloys, but, the decrease for 2024 alloy was more than the decreasing for 6061 alloy elongation. Therefore, from this study it can be concluded that the 2024 aluminum alloy is better than 6061 aluminum alloy, and, the modifying for its properties for 2024 aluminum alloy is better than for 6061 alloy.

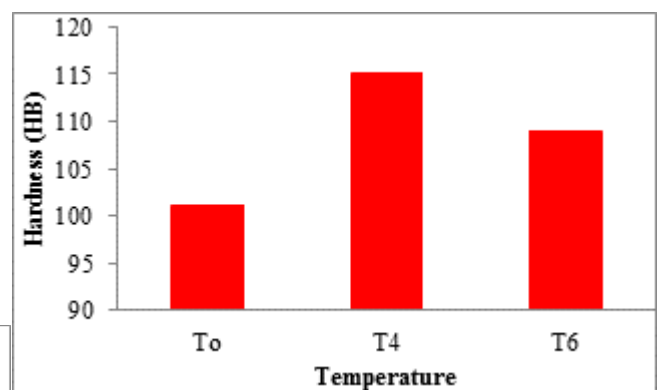


Figure 3. Hardness for 2024 Aluminum Alloy with Various Heat Treatment

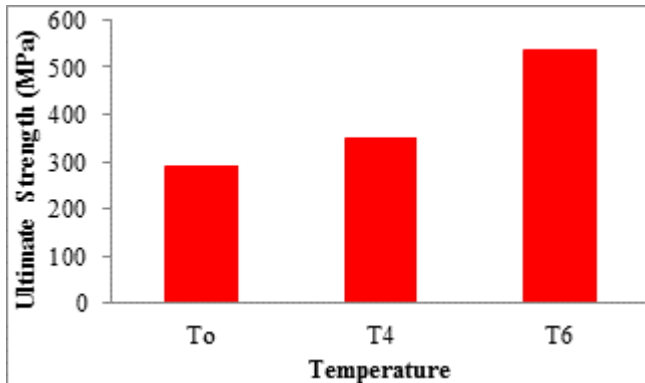


Figure 4. Hardness for 6061 Aluminum Alloy with Various Heat Treatment

Figure 5. Hardness Comparison Between Different Aluminum Alloy with Various Heat Treatment Effect

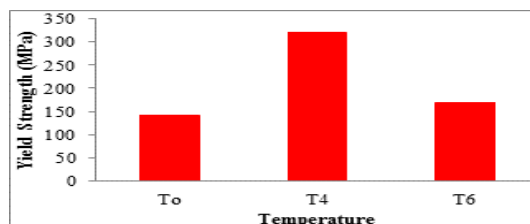


Figure 6. Yield Strength for 2024 Aluminum Alloy with Various Heat Treatment Effect


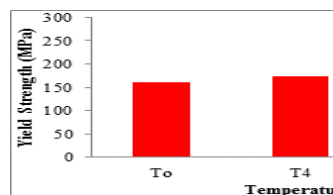


Figure 7. Yield Strength for 6061 Aluminum Alloy

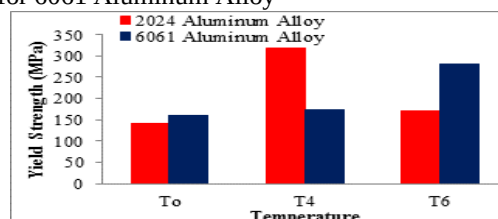

with Various Heat Treatment Effect

Figure 8. Yield Strength Comparison Between Different Aluminum Alloy with Various Heat Treatment Effect


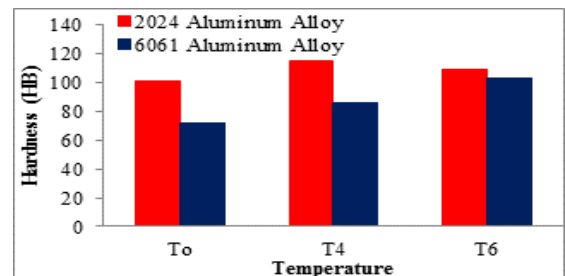


Figure 9. Ultimate Strength for 2024 Aluminum

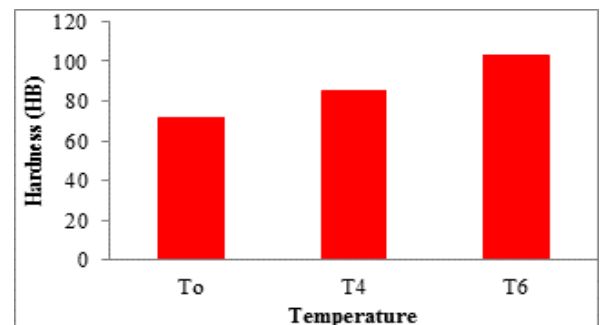

Alloy with Various Heat Treatment Effect

Figure 10. Ultimate Strength for 6061 Aluminum Alloy with Various Heat Treatment Effect

Figure 11. Ultimate Strength Comparison Between Different Aluminum Alloy with Various Heat Treatment Effect

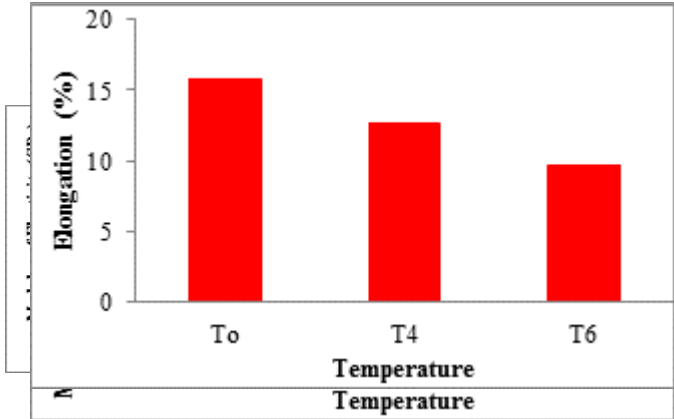


Figure 12. Modulus of Elasticity for 2024 Aluminum Alloy with Various Heat Treatment Effect

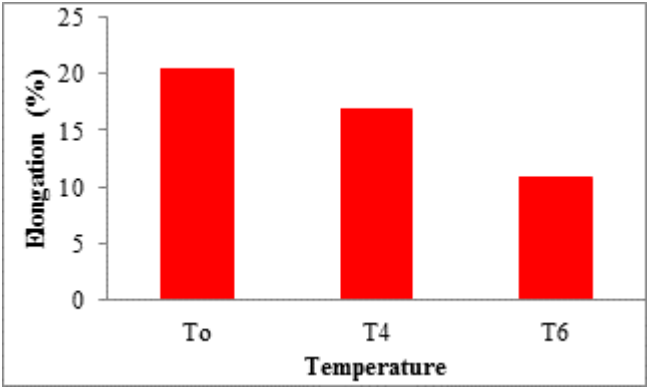


Figure 13. Modulus of Elasticity for 2024 Aluminum Alloy with Various Heat Treatment Effect

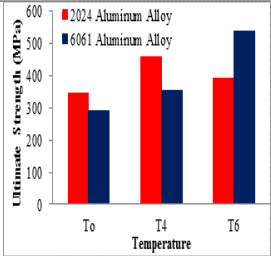


Figure 14. Modulus of Elasticity Comparison Between Different Aluminum Alloy with Various Heat

Treatment Effect

Figure 15. Elongation for 2024 Aluminum Alloy with Various Heat Treatment Effect

Figure 16. Elongation for 6061 Aluminum Alloy with Various Heat Treatment Effect


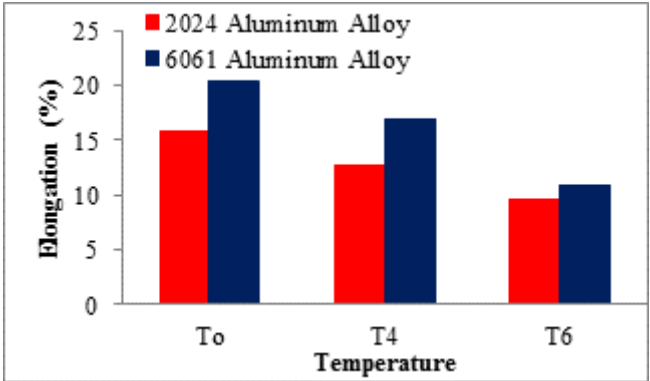


Figure 17. Elongation Comparison Between Different Aluminum Alloy with Various Heat Treatment Effect


The first part for dynamic characteristics include evaluating the natural frequency of the two types of alloys (2024 and 6061 aluminum alloy) with

various heat treatment effect. Thus, firstly, a comparison between the results evaluated by analytical solution with numerical and experimental results for simply supported plate, as

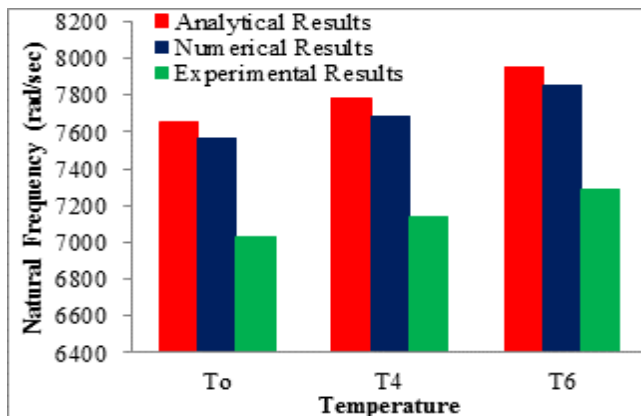

shown in Figs. 18 and 19, for 2024 and 6061 alloy materials, respectively. Then, a comparison between the natural frequencies for the two alloys with different heat treatment effect, as shown in Fig. 20. There, from this figure can it can be seen that modifying the natural frequency for 2024 alloy, with heat treatment, is better than modifying for 6061 alloy plate materials. In addition to this it can also be seen that the best temperature for 2024 alloy is T4 heat treatment.


Also, the behavior for cantilever plate structure

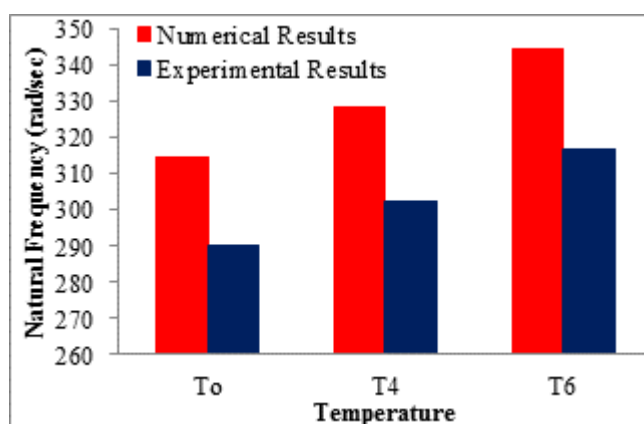

presented in Figs. 21 and 22 to show comparison between the numerical and experimental natural frequency results for two types of alloys with different heat treatments. The

effect of heat treatment on natural frequency for different alloy materials for plate structure is shown in Fig. 23. Where, from this figure it can be seen that the effect of heat treatment on the natural frequency is similar to the effect of heat

treatment on frequency for simply supported plate

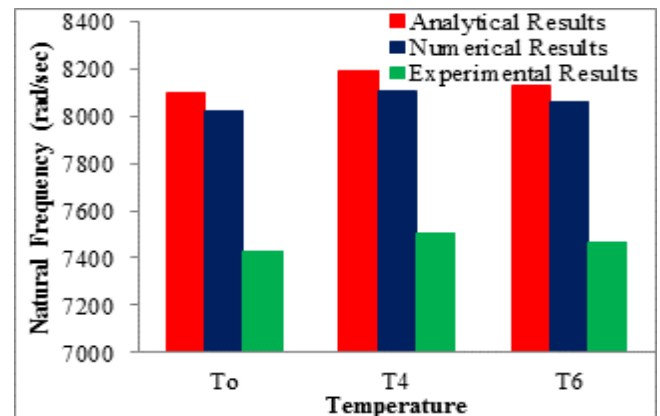

structure.

In addition, from Figs. 18 and 19, can be seen that the analytical, numerical and experimental results is in agreement with maximum error between analytical and numerical method and does not exceed around (1%), and the percentage error between analytical and experimental method is about (10%). Also, the comparison for numerical and experimental natural frequencies results presented in Figs. 21 and 22, for cantilever plate, show that the maximum error between its results are around (10%). Then, from the results presented we find that the 2024 aluminum alloy is better than the 6061 aluminum alloy and the modification for the 2024 alloy is better than that of the 6061 alloy with heat treatment effect.

Figure 18. Comparison of Natural Frequency for Simply Supported Plate of 2024 Aluminum Alloy, Evaluated by Different Techniques

Figure 19. Comparison of Natural Frequency for Simply Supported Plate of 6061 Aluminum Alloy, Evaluated by Different Techniques

Figure 20. Natural Frequency for Various Aluminum Alloy Simply Supported Plate, with Different Temperature Effect



Figure 21. Comparison of Natural Frequency for Cantilever Supported Plate of 2024 Aluminum Alloy, Evaluated by Different Techniques

Figure 22. Comparison of Natural Frequency for Cantilever Supported Plate of 6061 Aluminum Alloy, Evaluated by Different Techniques

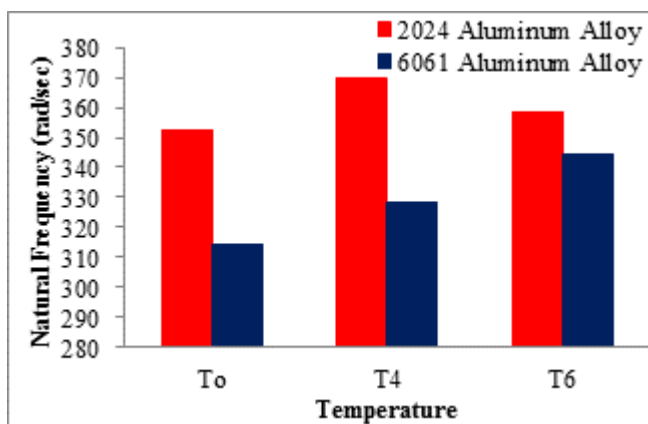



Figure 23. Natural Frequency for Various Aluminum Alloy Cantilever Supported Plate, with Different Temperature Effect

Time Plate Response

These results represent the second part of the dynamic characteristics for aluminum alloy structure with effect of heat treatment on its alloy. Figs, 24 to 29, for the two alloys with different heat treatment effect. Show that the analytical response results for simply supported plate structure with various materials used (2024 and 6061 aluminum alloy) are agreement with maximum error did not exceed (1.2%).

Then, after agreement evaluation for response results, presenting the effect for heat treatment on the maximum simply supported plate response for 2024 and 6061 aluminum alloy, as shown in Figs. 30 and 31, respectively, and comparing its response for 2024 and 6061 alloy plates, as shown in Fig. 32, with different heat treatment effect. Therefore, from the results presented in Figs. 30 to 32, we note that the response for plate structure decreases with heat treatment for the two alloys,

but, the decrease response for 2024 alloy plate is more than the decrease for 6061 alloy plate. Therefore, it can be conclusion that the modifying

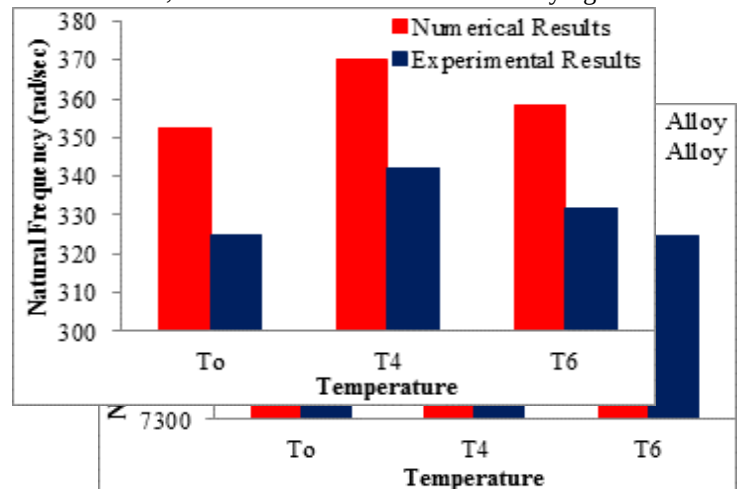

for 2024 alloy with heat treatment material is better than the modifying for 6061 alloy, with dependent on the dynamic response plate behavior.

Found that heat treating (2024 and 6061) alloys improves their mechanical properties and the dynamic behavior of these plates, thus the dynamic behavior of structures made from these alloys are improved when undergoing heat treatment. But the 2024 alloy is better than the 6061 alloy when heat treated.

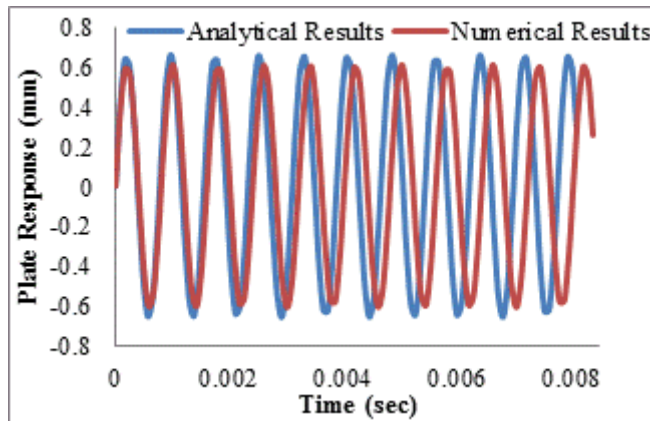


Figure 24. Comparison Between Analytical and Numerical Plate Response Results with To Temperature Effect of 2024 Aluminum Alloy

Figure 25. Comparison Between Analytical and Numerical Plate Response Results with T4 Temperature Effect of 2024 Aluminum Alloy

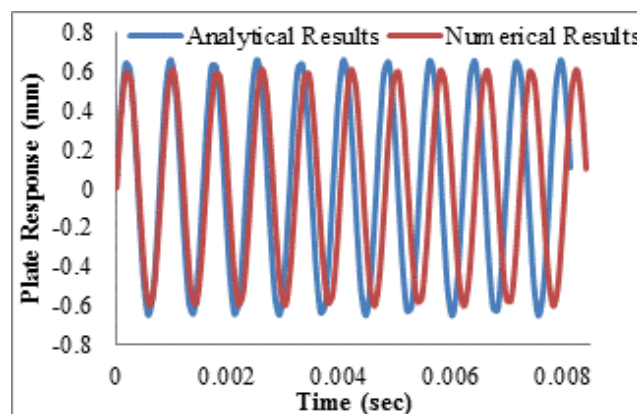
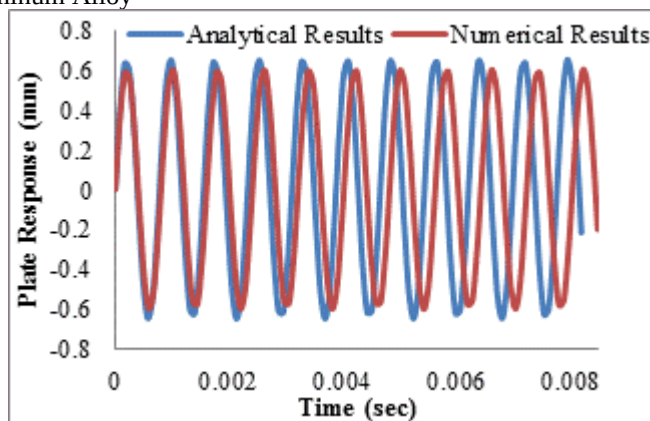


Figure 26. Comparison Between Analytical and Numerical Plate Response Results with T6 Temperature Effect of 2024 Aluminum Alloy

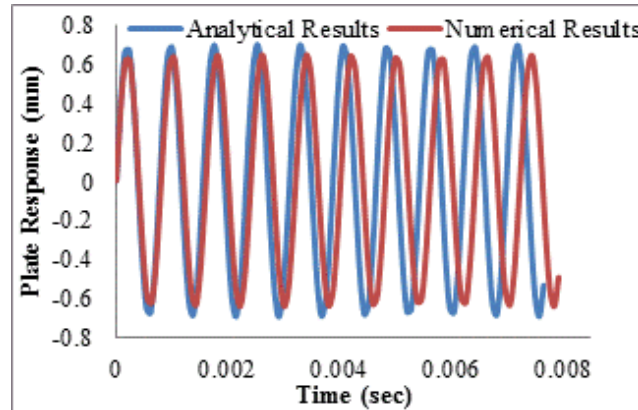


Figure 27. Comparison Between Analytical and Numerical Plate Response Results with T0 Temperature Effect of 6061 Aluminum Alloy

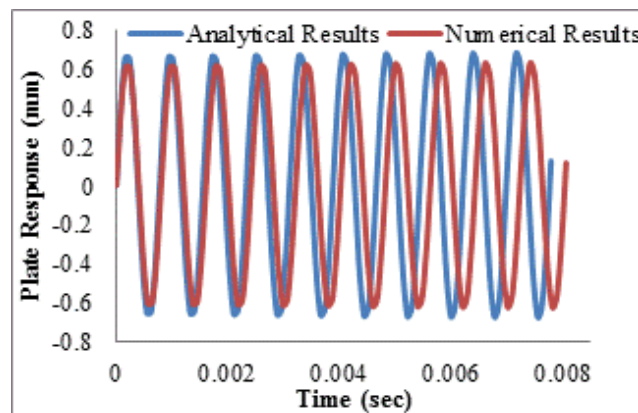


Figure 28. Comparison Between Analytical and Numerical Plate Response Results with T4 Temperature Effect of 6061 Aluminum Alloy

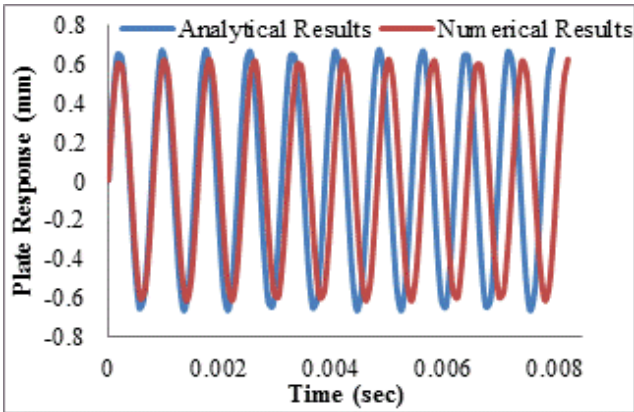


Figure 29. Comparison Between Analytical and Numerical Plate Response Results with T6 Temperature Effect of 6061 Aluminum Alloy

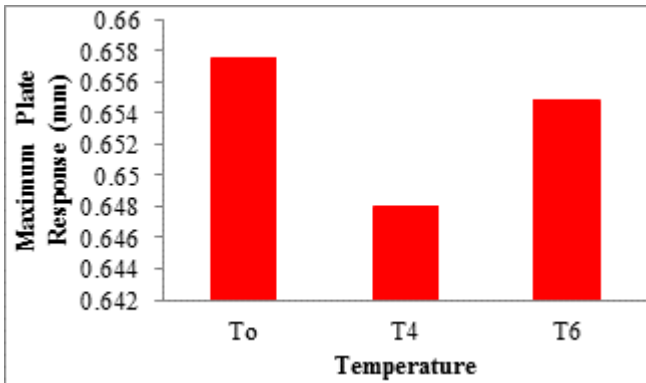


Figure 30. Maximum Plate Response with Different Temperature Effect for 2024 Aluminum Alloy, with Unit Impulse Load Effect

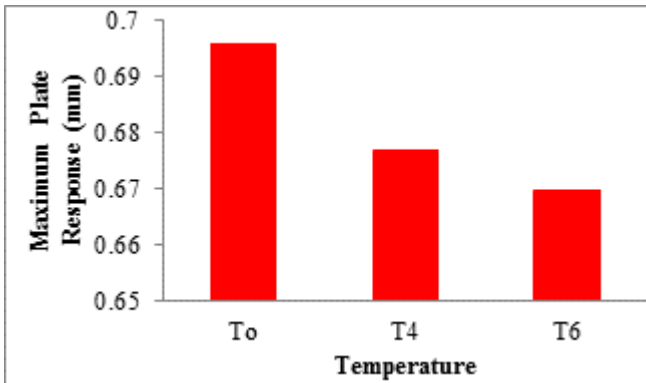


Figure 31. Maximum Plate Response with Different Temperature Effect for 6061 Aluminum Alloy, with Unit Impulse Load Effect

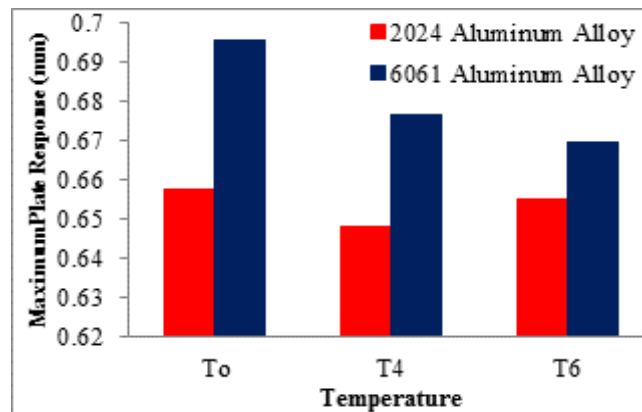


Figure 32. Maximum Plate Response for Various Aluminum Alloy with Different Temperature Effect, with Unit Impulse Load Effect

CONCLUSION

From the presenting work, the effect of heat treatment (To, T4, and T6) on the mechanical properties and dynamic characterizations for plate structure of 2024 and 6061 aluminum alloy materials, can be conclusion the following important points, as

Heat treatment modifies the mechanical properties for aluminum alloy materials, where, the best temperature treatment for 2024 alloy is T4 and T6 for 6061 alloy.

The mechanical properties for 2024 aluminum alloy material is better than mechanical properties for 6061 aluminum materials., also modifying the mechanical properties of 2024 alloy by heat treatment is better than the modification of the mechanical properties for 6061 alloy.

The dynamic characteristics for simply supported and cantilever plate structure made of 2024 and 6061 aluminum alloy materials can be modified by the use of heat treatment.

The dynamic characteristics for 2024 alloy plate are better than the dynamic characteristics for 6061 alloy materials plate structure, for different supported and various heat treatment effects.

The analytical solution technique is a perfect solution and can be used to evaluate the dynamic characteristics (natural frequency and response) for simply supported plate structure, with different

parameters effect on the mechanical properties of plate materials.

The comparison between analytical, numerical and experimental techniques used for evaluating the natural frequency for plate structure gave good results with accepted percentage error. Also, the comparison between numerical and experimental plate response results gave a good agreement for its results.



REFERENCES

- [1] E. Tan, B. Ogel. "Influence of Heat Treatment on the Mechanical Properties of AA6066 Alloy". *Turkish Journal of Engineering and Environmental Sciences*, Vol. 31, pp. 53-60, 2007.
- [2] M.R. Khan, Irfanullah, F. ur-Rehman. "Beneficial Effect of Heat Treatment on Mechanical Properties and Microstructure of Aluminum Alloys used in Aerospace Industry", *Journal of Pakistan Materials Society*, Vol. 02, No. 01, 2008.
- [3] G. Mrówka-Nowotnik. "Influence of chemical composition variation and heat treatment on microstructure and mechanical properties of 6xxx alloys". *Archives of Materials Science and Engineering*, Vol. 46, No. 02, pp. 98-107, 2010.
- [4] D. J. Chakrabarti, D. E. Laughlin. "Phase relations and precipitation in Al–Mg–Si alloys with Cu additions". *Progress in Materials Science*, Vol. 49, No. 3-4, pp. 389-410, 2004.
- [5] L. Zehn, S. B. Kang, H. W. Kim. "Effect of Natural Aging and Preaging on Subsequent Precipitation Process of an Al-Mg-Si Alloy with High Excess Silicon". *Materials Science and Technology*, Vol. 13, No. 11, pp. 905-911, 1997.
- [6] Y. Sun, M. Baydogan, H. Cimenoglu. "The Effect of Deformation Before Ageing on the Wear Resistance of an Aluminium Alloy". *Materials Letters*, Vol. 38, No. 03, pp. 221-226, 1999.
- [7] S.H. Ibrahim, S.H. Ahmed, I.A. Hameed. "Evaluated of Mechanical Properties for Aluminum Alloy using Taguchi Method International". *Journal of Modern Studies in Mechanical Engineering*, Vol. 02, No. 01, pp. 29-37, 2016.
- [8] G. Hussain, R.A. Khan. "Existence of Solution to A Boundary Value Problem of Hybrid Fractional Differential Equations Using Degree Method". *Matriks Sains Matematik*, vol. 1, no. 1, pp. 24-28, 2018.
- [9] X.C. Tian, Q.H. Li, C.S. He, Y.G. Cai, Y. Zhang, Z.G. Yang. "Design and experiment of reciprocating double Track Straight Line Conveyor". *Acta Mechanica Malaysia*, vol. 2, no. 2, pp. 01-04, 2018.
- [10] M.S. Ibrahim, S. Kasim, R. Hassan, H.N. Mahdin, A.A. Ramli, M.F. Md Fudzee, M.A. Salamat. "Information Technology Club Management System". *Acta Electronica Malaysia*, vol. 2, no. 2, pp. 01-05, 2018.
- [11] F. Qiao. "The Study on The Integration of Green Architecture and Appropriate Technology". *Engineering Heritage Journal*, vol. 2, no. 2, pp. 01-03, 2018.
- [12] P. Rambabu, N. E. Prasad, V. V. Kutumbarao, R. J. H. Wanhill. "Aluminium Alloys for Aerospace Applications". *Aerospace Materials and Material Technologies*, Vol. 01, 2017.
- [13] Military Standardization Handbook, *Aluminum and Aluminum Alloys*, MIL-HDBK-694A (MA), 1966.
- [14] Z.Y. Hussien, K.K. Resan. "Effects of Ultraviolet Radiation with and without Heat, on the Fatigue Behavior of Below-Knee Prosthetic Sockets", *International Journal of Mechanical and Production Engineering Research and Development (IJMPERD)*, Vol. 07, No. 06, 2017.
- [15] K.K. Resan, A. A. Alasadi, M. Al-Waily, M. J. Jweeg, "Influence of Temperature on Fatigue Life for Friction Stir Welding of Aluminum Alloy Materials". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 18, No. 02, 2018.
- [16] M. J. Jweeg, M. Al-Waily, A. K. Muhammad, K. K. Resan. "Effects of Temperature on the Characterisation of a New Design for a Non-Articulated Prosthetic Foot". *IOP Conference Series: Materials Science and Engineering, 2nd International Conference on Engineering Sciences, Kerbala, Iraq*, Vol. 433, pp. 26–27 March 2018.



- [17] L. E. Yousif, K. K. Resan, R. M. Fenjan. "Temperature Effect on Mechanical Characteristics of A New Design Prosthetic Foot". *International Journal of Mechanical Engineering and Technology (IJMET)*, Vol. 09, No. 13, pp. 1431-1447, 2018.
- [18] M. A. Al-Shammari, S. E. Abdullah. "Stiffness to Weight Ratio of Various Mechanical and Thermal Loaded Hyper Composite Plate Structures". IOP Conference Series: Materials Science and Engineering, *2nd International Conference on Engineering Sciences*, Vol. 433, 2018.
- [19] ASM Handbook, Heat Treating, ASM International, *The Materials Information Company*, Vol. 04, 1991.
- [20] M. K. Abbass, H. A. Ameen, K. S. Hassan. "Effect of heat treatment on corrosion resistance of friction stir welded AA 2024 aluminum alloy". *American Journal of Scientific and Industrial Research*, Vol. 02, No. 02, pp 297-306, 2011.
- [21] B. A. Bedaiwi, J. S. Chiad. "Vibration analysis and measurement in the below knee prosthetic limb part I: Experimental work". *ASME 2012 International Mechanical Engineering Congress and Exposition, Proceedings (IMECE)*, 2012.
- [22] A. M. Takhakh, F. M. Kadhim, J. S. Chiad. "Vibration Analysis and Measurement in Knee Ankle Foot Orthosis for Both Metal and Plastic KAFO Type". *ASME 2013 International Mechanical Engineering Congress and Exposition IMECE 2013*, November 15-21, San Diego, California, USA, 2013.
- [23] A. Alhumdany, M. Al-Waily, M.H.K. Al-Jabery. "Theoretical and Experimental Investigation of Using Date Palm Nuts Powder into Mechanical Properties and Fundamental Natural Frequencies of Hyper Composite Plate". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 16, No. 01, 2016.
- [24] M. J. Jweeg, E. Q. Hussein, K. I. Mohammed. "Effects of Cracks on the Frequency Response of a Simply Supported Pipe Conveying Fluid". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 17, 05, 2017.
- [25] H. J. Abbas, M. J. Jweeg, M. Al-Waily, A. A. Diwan. "Experimental Testing and Theoretical Prediction of Fiber Optical Cable for Fault Detection and Identification". *Journal of Engineering and Applied Sciences*, Vol. 14, No. 02, pp. 430-438, 2019.
- [26] L.S. Al-Ansari, M. Al-Waily, A. M. H. Yusif. "Vibration Analysis of Hyper Composite Material Beam Utilizing Shear Deformation and Rotary Inertia Effects". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 12, No. 04, 2012.
- [27] M. J. Jweeg. "A Suggested Analytical Solution for Vibration of Honeycombs Sandwich Combined Plate Structure". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 16, No. 02, 2016.
- [28] M. Al-Waily, K. K. Resan, A. H. Al-Wazir, Z. A. A. Abud Ali. "Influences of Glass and Carbon Powder Reinforcement on the Vibration Response and Characterization of an Isotropic Hyper Composite Materials Plate Structure". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 17, No. 06, 2017.
- [29] M. Al-Waily, M. A.R. Sadiq Al-Baghdadi, R. H. Al-Khayat. "Flow Velocity and Crack Angle Effect on Vibration and Flow Characterization for Pipe Induce Vibration". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 17, No. 05, pp.19-27, 2017.
- [30] M. A. Al-Shammari. "Experimental and FEA of the Crack Effects in a Vibrated Sandwich Plate". *Journal of Engineering and Applied Sciences*, Vol. 13, No. 17, pp. 7395-7400, 2018.
- [31] E. N. Abbas, M. J. Jweeg, M. Al-Waily. "Analytical and Numerical Investigations for Dynamic Response of Composite Plates Under Various Dynamic Loading with the Influence of Carbon Multi-Wall Tube Nano

- Materials". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 18, No. 06, pp. 1-10, 2018.
- [32] M. J. Jweeg, M. Al-Waily, A. A. Deli. "Theoretical and Numerical Investigation of Buckling of Orthotropic Hyper Composite Plates". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 15, No. 04, 2015.
- [33] M. Al-Waily, Z. A. A. Abud Ali. "A Suggested Analytical Solution of Powder Reinforcement Effect on Buckling Load for Isotropic Mat and Short Hyper Composite Materials Plate". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 15, No. 04, 2015.
- [34] M. A. Al-Shammari, M. Al-Waily. "Analytical Investigation of Buckling Behavior of Honeycombs Sandwich Combined Plate Structure". *International Journal of Mechanical and Production Engineering Research and Development (IJMPERD)*, Vol. 08, No. 04, pp. 771-786, 2018.
- [35] S. S. Rao 'Vibration of Continuous System' John Wiley & Sons, Inc., 2007.
- [36] M. J. Jweeg, A. S. Hammood, M. Al-Waily. "A Suggested Analytical Solution of Isotropic Composite Plate with Crack Effect". *International Journal of Mechanical & Mechatronics Engineering IJMME- IJENS*, Vol. 12, No. 05, 2012.
- [37] M. A. Al-Shammari, M. Al-Waily. "Theoretical and Numerical Vibration
- Investigation Study of Orthotropic Hyper Composite Plate Structure". *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 14, No. 06, 2014.
- [38] S. S. Rao. "Mechanical Vibration". *Sixth Edition, Pearson Education, Inc.*, 2018.
- [39] M. J. Jweeg, A. S. Hammood, M. Al-Waily. "Experimental and Theoretical Studies of Mechanical Properties for Reinforcement Fiber Types of Composite Materials", *International Journal of Mechanical & Mechatronics Engineering IJMME-IJENS*, Vol. 12, No. 04, 2012.
- [40] A. Taher, A. M. Takhakh, S. M. Thaha. "Experimental Study and Prediction the Mechanical Properties of Nano-Joining Composite Polymers", *Journal of Engineering and Applied Sciences*, Vol. 13, No. 18, pp. 7665, 7669, 2018.
- [41] M. J. Jweeg. "Application of finite element analysis to rotating fan impellers", *Doctoral Thesis*, Aston University, 1983.
- [42] M. A. Al-Shammari, L. Y. Zedan, A. M. Al-Shammari. "FE simulation of multi-stage cold forging process for metal shell of spark plug manufacturing", *1st International Scientific Conference of Engineering Sciences-3rd Scientific Conference of Engineering Science, ISCES 2018- Proceedings*, 2